

IMPROVEMENT OF ENGINEERING PROPERTIES OF FIRED CLAY BRICKS THROUGH THE ADDITION OF CALCITE



Dr. Fernando Martirena, Univ. Central de las Villas, Cuba

Dr. Robert L. Day, University of Calgary, Canada

AIM OF THE WORK




To lower the firing temperature as a means to reduce energy consumption in fired clay bricks production



To increase compressive strength of the bricks in order to improve mechanical properties and manufacture lighter bricks (thinner walls)

CALCITE AS FLUXING AGENT

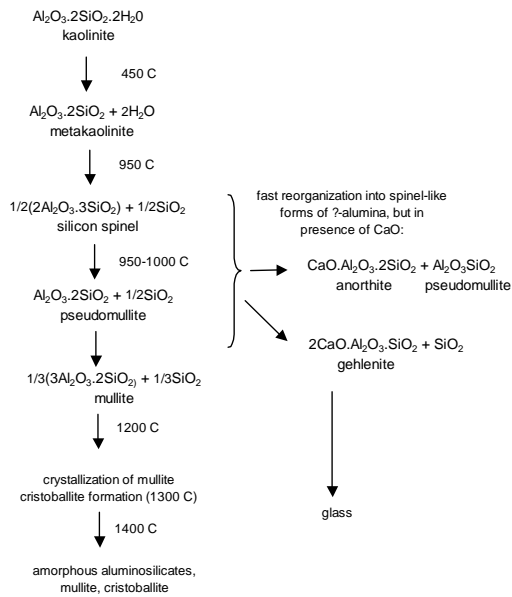

MECHANISM OF ACTION

The fluxing action of calcite on clay minerals is described in the paper presented by Mayoral et al at "Thermochimica Acta"^[1]. The paper is based on the study of the mechanisms of decomposition of kaolinite and the ternary system $\text{CaO} \cdot \text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2$. The research was conducted on fly ash resulting from coal combustion, whose chemical composition is very similar to clay minerals, mainly aimed at studying the influence of calcite and sintering time over the reactions of aluminosilicates in solid state.

[1] M.C Mayoral et al: Aluminosilicates transformations in combustion followed by DSC", Thermochimica Acta 373 (2001), pp 173-180

PREVIOUS EXPERIENCES

PHYSICAL BEHAVIOUR OF HAND-MADE BRICKS WITH ADDITIVES

Cultrone G.⁽¹⁾, Sebastián E.⁽¹⁾, de la Torre M.J.⁽²⁾, Linares L.⁽¹⁾

(1) Dep. Mineralogy and Petrology, University of Granada (Spain)
 (2) Dep. Geology, University of Jaén (Spain)

RESULTS

At 800 °C the samples without additives (G) still maintain the laminar habit of the phyllosilicates. At 900 °C the phyllosilicates deform and tend to clump. At 1000 °C the surface become smoother and the pores assume ellipsoidal form with smooth edges. In the samples with additives at 800 °C the phyllosilicates layers loose the plane-parallel disposition and assume a rosette morphology. At 900 °C the pores show angular morphology and only few indications of vitrification are observed. At 1000 °C the bricks with salt (GS) are vitrified, while those with carbonates (GC and GD) have not modified their texture.

CONCLUSIONS

- 1) The presence of additives in the raw material, even in small quantities, modify the characteristics of the ceramic products.
- 2) Carbonates favour a high vitrification at low firing temperatures (800 and 900 °C). This vitrification should improve the quality of the bricks, but is counteracted by the increase of porosity and the capacity of water absorption.
- 3) The best hydric and ultrasonic results correspond to the bricks without additives or with salt and fired at 1000 °C because they are the most vitrified and, therefore, the most resistant to physical and mechanic stress.

The experiences listed in the literature associate the presence of calcium carbonate with both higher vitrification at lower temperatures and the increase of porosity and water absorption ...

SPECIMEN PREPARATION





Cylinders with 3.5 mm diameter were cast in molds; Moulding pressure was 7 MPa. The cylinders were dried for 3-5 days and then fired in an electric oven. Firing was done in two stages: a) removing combined water up to 500 C, and b) Elevated temperature firing. Real bricks were also cast and fired in the same conditions



Testing procedure

- Compressive strength
- Water absorption
- Density
- Shrinkage
- Dimension changes
- Twisting
- Microstructural analysis

EXPERIMENTAL WORK: CYLINDERS

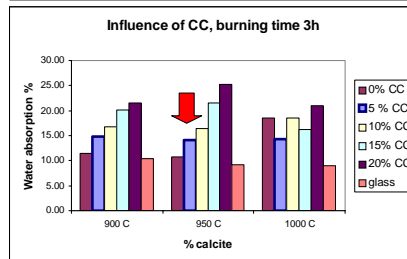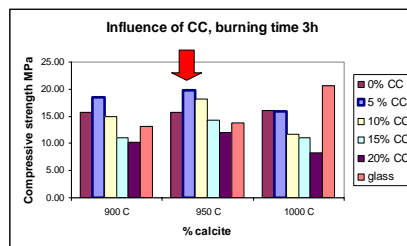

FIRST SET OF TESTS

Proportions admixture/clay:
0:100, 5/95, 10/90,
15/85, and 20/80

Burning time: 3 h


Burning temperature: 900 C,
950 C, 1000 C

These tests showed: (a) That calcite appears to modify the mineralogical properties of the bricks, (b) The lower the amount of calcite, the better the impact...




We decided to lower the amount of calcite



EXPERIMENTAL WORK: CYLINDERS

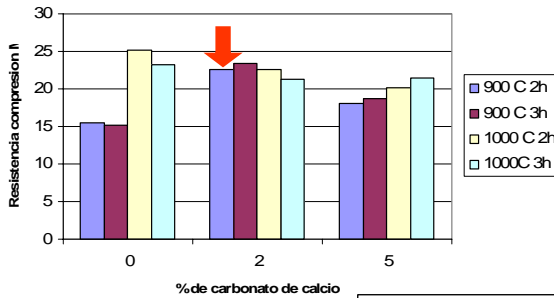

900 °C / 1000 °C were chosen as the most relevant temperatures. The best results were accomplished in bricks fired at 900 C with 2% calcium carbonate. Water absorption was improved. Firing temperature does not seem to influence in the range evaluated (2-3 hours)

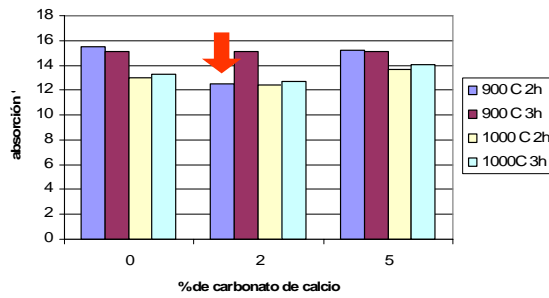


EXPERIMENTAL WORK: REAL BRICKS

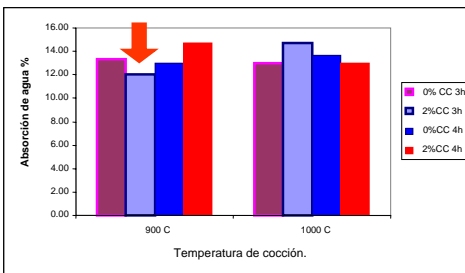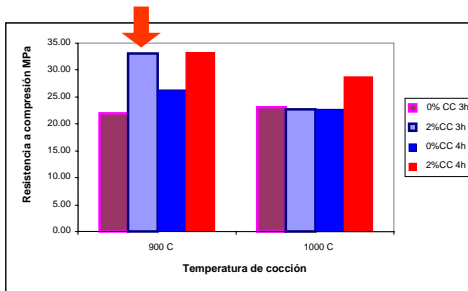


The experimental results obtained in cylinders were replicated in real bricks. The bricks fired at 900 C attained a higher compressive strength and a lower water absorption. No influence of firing temperature

MICROSTRUCTURAL ANALYSIS: MIP

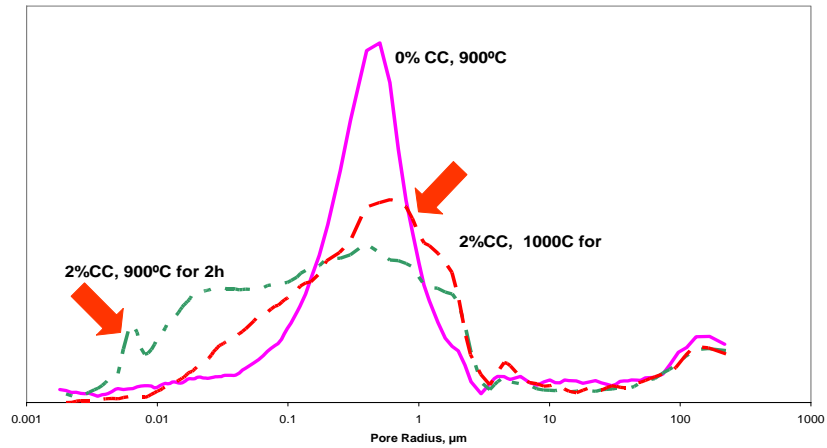


MIP tests showed no major differences in porosity between all the samples tested. Smaller pores (0.05-0.08) formed again in samples made with calcium carbonate admixture.


MICROSTRUCTURAL ANALYSIS: MIP

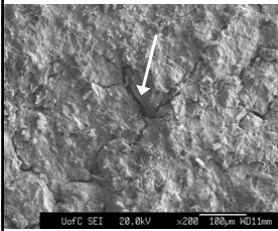


In sample M3 (1000 C, 2% CC), mayor cracks were observed, probably caused by the transition from CaO to Ca(OH)₂

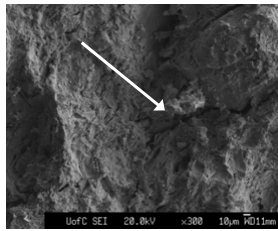

Similar cracks were observed at sample M6 (900 C, 5% CC), also some stretched pores, as described in the literature*

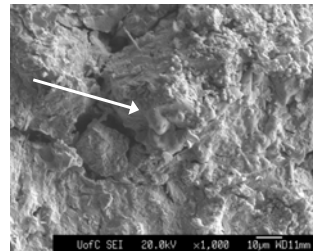

SEM picture of sample M3 shows evident signs of glass melting

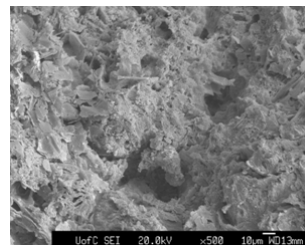


SEM picture of sample M2 shows typical phyllosilicates structures densely organized

* Cultrone G. et al, Behaviour of brick samples in aggressive environments. Water, air and soil pollution 119: 191-207, 2000

Samp. ID	Burning temp.	% of C. Carbon.	Burning time
M-1 (bricks made in Cuba)	900 C	0	2h
M-2 (bricks made in Cuba)	900 C	2%	2h
M-3 (bricks made in Cuba)	1000 C	2%	2h
M-4 (bricks made in Cuba)	900 C	0%	3h
M-5 (bricks made in Cuba)	900 C	2%	3h
M-6 (bricks made in Cuba)	900 C	5%	3h
M-7 (FA bricks made in Canada)	900 C		

MINERALOGICAL TRANSFORMATIONS: XRD

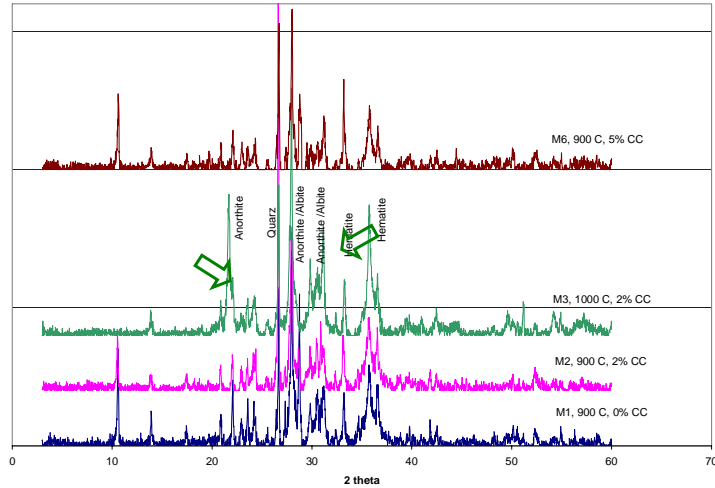

Anorthite only appears in specimens made with calcium carbonate and fired at 1000 C.

DURABILITY TESTING

ID	% clay	% cc	Temp	T (h)
MP1	100	0	900 C	3h
D1(M2)	95	5	900 C	3h
MP2	100	0	900 C	4h
D2(M6)	95	5	900 C	4h
MP3	100	0	1000 C	3h
D3(M4)	95	5	1000 C	3h
MP4	100	0	1000 C	4h
D4(M8)	95	5	1000 C	4h
MP5	100	0	900 C	3h
D5(M3-1)	95	2	900 C	3h
MP6	100	0	900 C	4h
D6(M3-2)	95	2	900 C	4h
MP7	100	0	1000 C	3h
D7(M3-3)	95	2	1000 C	3h
MP8	100	0	1000 C	4h
D8(M3-4)	95	2	1000 C	4h

Testing procedure

Wet/Dry cycles: (24 hours) in three phases: immersion in water for 16 hours at room temperature (20 C), forced desiccation in an oven at 100 C for 6 hours and cooling at room temperature (20 C) for 2 hours.

Crystallization: (24 hours) in three phases: immersion in se NaSO₄ x 10H₂O (14%) (20°C) for 4 hours, oven drying at 100 C for 16 hours, and cooling at room temperature (20 C) for 4 hours.



These tests could be conclusive for the final application of the results in practice

DURABILITY TESTING: WET & DRY CYCLES



T: 900 C, 3 h burning, control series (right) and sample made with 5% calcium carbonate



T: 900 C, 4 h burning, control series (right) and sample made with 5% calcium carbonate



T: 1000 C, 3 h burning, control series (right) and sample made with 5% calcium carbonate

The **wet-dry cycles** did not give significant differences between the control series and the bricks manufactured with different amounts of calcium carbonate

DURABILITY TESTING: SALT CRYSTALLIZATION



T: 900 C, 3 h burning, control series (right) and sample made with 5% calcium carbonate



T: 900 C, 4 h burning, control series (right) and sample made with 5% calcium carbonate



T: 1000 C, 4 h burning, control series (right) and sample made with 5% calcium carbonate

The **crystallization tests** did also not give significant differences between the control series and the bricks manufactured with different amounts of calcium carbonate

PRACTICAL APPLICATIONS: BRICK YARD



The trials were done in a typical brick yard in Cuba...

PRACTICAL APPLICATIONS: BRICK YARD

	Compressive strength MPa	Firing time	Firewood savings kg
Without calcium carbonate	14.6	10 h	-
With calcium carbonate	17.0	5 h	3200

The trials showed that there is a tremendous potential to optimize the production of bricks in the developing world...

PRACTICAL APPLICATIONS: INDUSTRY

1



2



3




4



We decided to prove this idea further in the modern brick industry...

PRACTICAL APPLICATIONS: INDUSTRY

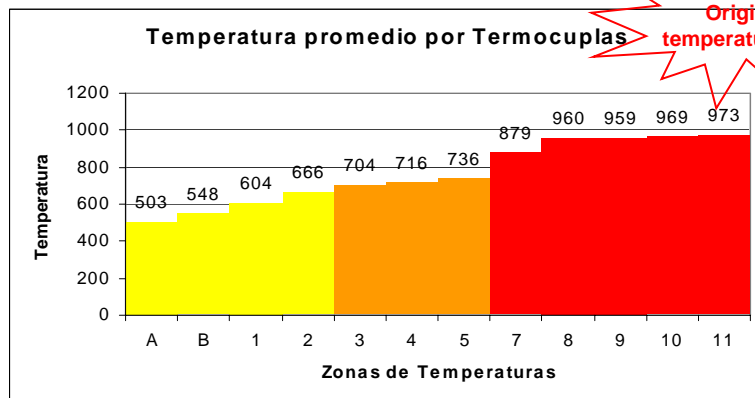

Cost difference	Fuel saved per hour of operation	Compressive strength sample with admixture	Compressive strength sample without admixture
18%	270 liters/h	2.6 MPa.	2.0 MPa.

CONCLUDING REMARKS

The addition of calcium carbonate (under 5%) to the clay used to manufacture fired clay bricks increases their compressive strength in the range of 30-50% when the bricks are fired at 900°C.

Adding CC brings about an increase of the amount of small pores (pores having radius under 1 μm) in all bricks where CC is added. These pores result from the formation of CaO, and the microcracks produced during the expansion caused by the hydration of CaO.

The main new phase formed as a result of firing is anorthite, which is a component in bricks fired at 1000°C.

The durability tests performed on real bricks made with CC proportion less than 5% appear to indicate that adding CC does not contribute to weakening of the brick matrix during exposure to an aggressive environment.

The idea was implemented at full scale production with outstanding results